

The role of rigidity in controlling material failure

Michelle M. Driscoll^{a,b,1}, Bryan Gin-gé Chen^{c,1}, Thomas H. Beuman^c, Stephan Ulrich^c, Sidney R. Nagel^{a,b}, and Vincenzo Vitelli^{c,2}

^aThe James Franck Institute, The University of Chicago, Chicago, IL; ^bDepartment of Physics, The University of Chicago, Chicago, IL; and ^cInstituut-Lorentz, Universiteit Leiden, 2300 RA Leiden, The Netherlands

Edited by Leonard Sander, University of Michigan, Ann Arbor, MI, and accepted by Editorial Board Member Herbert Levine July 25, 2016 (received for review January 22, 2015)

We investigate how material rigidity acts as a key control parameter for the failure of solids under stress. In both experiments and simulations, we demonstrate that material failure can be continuously tuned by varying the underlying rigidity of the material while holding the amount of disorder constant. As the rigidity transition is approached, failure due to the application of uniaxial stress evolves from brittle cracking to system-spanning diffuse breaking. This evolution in failure behavior can be parameterized by the width of the crack. As a system becomes more and more floppy, this crack width increases until it saturates at the system size. Thus, the spatial extent of the failure zone can be used as a direct probe for material rigidity.

failure | metamaterials | jamming | cracks | glasses

Brittle solids typically fail suddenly and catastrophically under an applied load; an initially microscopic crack will rapidly grow and quickly traverse the entire sample, breaking it into two. At the tip of this crack, the stress applied at the boundaries is highly focused into a small region, often termed the “failure process zone.” It is in this small region that the rupturing and breaking of bonds actually occurs; in this zone, which generally depends on material toughness (1, 2), dissipation and nonlinearities dominate the dynamics (3, 4). Outside of this zone, linear elasticity characterizes the medium’s response. In very rigid solids, the process zone is microscopic, and the highly nonlinear dynamics within it are difficult to observe. However, the size of the process zone increases vastly if sufficient disorder is present (5–7). Thus, disorder is one relevant parameter for describing the nature of solid failure under tension.

In this work, we demonstrate that mechanical rigidity is another equally important parameter that controls material failure. The spatial extent of the process zone under loading is large for marginally rigid solids [e.g., materials that lie close to a rigidity transition (8–13)]. Examples of a marginally rigid solid include sparsely connected disordered elastic networks, loose granular packings, and cellular materials constructed from slender beams. In all of these cases, the loss of rigidity is signaled by the vanishing of a linear elastic modulus.

Using rigidity as a control parameter, we can dramatically change how a material fails. As illustrated in Fig. 1 *A–C*, it is evident that there are two distinct effects that give rise to a broadened failure zone. First, we note that, due to disorder, even an ordinary thin crack (Fig. 1*A*) will meander horizontally in the direction transverse to the pulling direction as the crack traverses the sample. This meandering gives rise to a failure zone that, although thin at each point along its trajectory, fluctuates in the vertical direction parallel to the applied stress. The second effect, which is the subject of the current paper, is that the intrinsic width of the failure zone grows as the rigidity of the sample is reduced as seen in Fig. 1*B*. Thus, diffuse broken bonds vertically span a region around the center of the failure zone (perpendicular to the pulling direction). We define the intrinsic width as the distribution of breaks about the centerline of the failure zone. As the intrinsic width of the failure zone grows, it dominates over the effect of meandering; the effect of meandering is no longer visible until the transverse width of the sample is much larger than

the intrinsic width of the crack. With decreasing rigidity, the crack width, and hence the process zone, continuously grows until it engulfs the entire sample, as seen in Fig. 1*C*. This effect appears to be quite robust. We find that the crack width can be tuned via rigidity in several distinctly different systems. In all of the cases that we examine here, thin cracks in rigid systems turn into broad, diffusive failure as the initial, unstressed, system is prepared to be closer to a rigidity transition.

Model Systems and Breaking Protocols

We study three distinct systems whose rigidity, measured by different geometric parameters, can be systematically controlled before the application of stress. By comparing these three systems, we can isolate effects due to the material’s geometry from those due to disorder. Thus, we can rule out that the observed behavior is solely due to changes in the degree of disorder.

The first system, illustrated in Fig. 1, is a simulation of a 2D ($D=2$) disordered network of point masses connected by unstretched springs of equal stiffness whose average coordination z can be varied. Such a network is at the isostatic threshold when $z=z_c=2D=4$. At the isostatic point, the number of constraints just balance the number of degrees of freedom so that the network is poised on the brink of failure; if there are no redundant constraints, then the removal of just one bond creates a zero-frequency normal mode of vibration (14). Networks at nonzero $\Delta z \equiv z - z_c$ are prepared by randomly removing the bonds with highest coordination from an initial, highly compressed, jammed packing of spheres until the target z is attained (see refs. 15 and 16 for details). This preparation procedure ensures that, upon lowering the geometric control parameter $r_1 \equiv \Delta z$, both G and B become vanishingly small, whereas their ratio, as well as the amount of disorder, remains constant.

Our second system is a simulation of a perturbed square lattice of point masses connected by equal-stiffness harmonic springs. (The nodes of this square lattice are displaced from those of a

Significance

As a solid approaches a rigidity transition, its failure behavior changes dramatically: cracks become wider and wider until their width reaches the system size. In this regime, bonds initially break at apparently random positions until they produce a percolating cluster spanning across the sample. Because the spatial extent of the failure process zone depends on material toughness, varying the rigidity can be used as a lens to examine the nonlinear response that would otherwise be observable only on a microscopic scale in a rigid material.

Author contributions: M.M.D., B.G.-g.C., S.R.N., and V.V. designed research; M.M.D., B.G.-g.C., T.H.B., S.U., S.R.N., and V.V. performed research; M.M.D., B.G.-g.C., T.H.B., S.U., S.R.N., and V.V. analyzed data; and M.M.D., B.G.-g.C., S.R.N., and V.V. wrote the paper.

The authors declare no conflict of interest.

This article is a PNAS Direct Submission. L.S. is a Guest Editor invited by the Editorial Board.

Freely available online through the PNAS open access option.

¹M.M.D. and B.G.-g.C. contributed equally to this work.

²To whom correspondence should be addressed. Email: vitelli@lorentz.leidenuniv.nl.

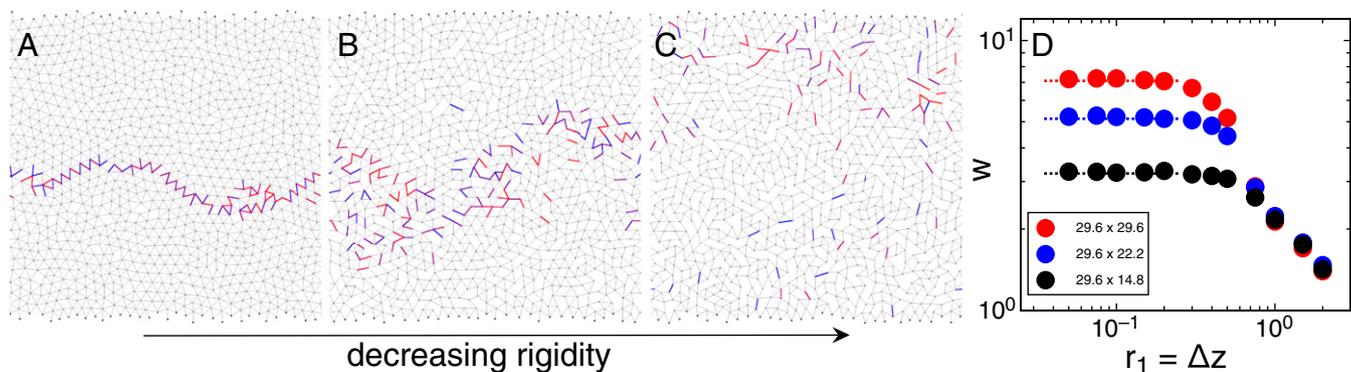


Fig. 1. Transition in material failure due to changing material rigidity. As bonds between nodes are removed from a random spring network, the failure behavior changes continuously from brittle cracking to diffuse breaking. In A–C, the sample is stressed uniaxially in the vertical direction. (A) A thin crack is observed in a rigid material. Only a small amount of meandering occurs. (B) The intrinsic width of the crack grows as the material becomes less rigid. (C) The crack width saturates at the size of the system when the rigidity of the material decreases toward the limit where the bulk and shear moduli vanish. (D) The width of the zone in which failure occurs, w , increases continuously as the rigidity, $r_1 \equiv \Delta z$, decreases and plateaus at a value w_0 , indicated by the dotted line. Once the crack width reaches the system size, only diffuse breaking occurs. The sample sizes are indicated in the legend: the horizontal width of the sample (perpendicular to the direction of applied stress) is kept constant at 29.6 and its vertical length (parallel to the pulling direction) varies from 14.8 to 29.6 (measured in units of the average interparticle spacing). Simulations use dissipative Newtonian dynamics, as detailed in *Model Systems and Breaking Protocols*.

perfect crystal by a small random vector $0.1s$, where s is the lattice spacing.) Here, the rigidity parameter is again $r_1 \equiv \Delta z$. This parameter counts additional springs (braces) added randomly along the diagonals (17). The completely ordered square lattice without braces at $\Delta z = 0$ is isostatic and has a vanishing shear modulus, G , and a finite bulk modulus, B . However, in our slightly disordered network, B drops to zero, as does G . Because each diagonal spring acts as an “impurity,” the disorder in the local connectivity varies with Δz .

In both of these simulation systems, periodic boundary conditions are applied in the direction perpendicular to the uniaxial pulling direction. Our numerical results are not sensitive to the choice of lateral boundary conditions for sufficiently large samples. The samples are pulled quasistatically, and springs are removed whenever they are strained above a specified threshold value. The quasistatic dynamics are obtained using two protocols: (i) in the random networks, we explicitly solve Newton’s equations in the presence of microscopic dissipation, as detailed in ref. 15; (ii) in the square system, we compute the linear response to an applied tension and remove the spring under the maximum stress before repeating. The process is stopped in the first protocol when the sample breaks into two parts and in the second protocol when the relevant linear elastic modulus drops to zero.

Our third example is an experimental system consisting of a macroscopic, weakly disordered, honeycomb lattice that is pulled uniaxially. The lattice structure, laser-cut from plastic sheets, is characterized by the ratio of strut width, x , to strut length, a . As in the braced square system, the nodes are displaced from those of a perfect lattice by random vectors with magnitude less than $0.1s$, where s is the spacing of the underlying lattice. The honeycomb lattice, with a coordination number $z = 3$, is overconstrained if both bond bending and central forces are present but is underconstrained if only central forces are considered. One can tune the rigidity of this metamaterial by lowering the aspect ratio of the struts, x/a . The bending energy and shear modulus G are proportional to $(x/a)^3$, whereas the stretching energy and bulk modulus B are proportional to x/a (18). The parameter $r_2 \equiv \sqrt{G/B}$ controls rigidity without altering structural disorder. This definition of r_2 was chosen so that $r_2 \propto x/a$ for the honeycomb lattice. As $r_2 \rightarrow 0$, the honeycomb lattice can increasingly accommodate compressions by beam-bending rather than stretching. For comparison, we have also studied triangular lattices with $z = 6$ where r_2 does not measure rigidity. The triangular lattice, as distinct from the

honeycomb lattice, remains rigid as $x/a \rightarrow 0$ so that G/B remains nearly constant as x/a is varied.

In the experimental study, the side edges (perpendicular to the direction of pulling) are free. The loading is applied using a strain-controlled translation stage (at a fixed displacement rate of $83 \mu\text{m/s}$) while the spatial distribution of the broken bonds is recorded using a high-speed camera (at rates varying from 10 fps to 190,000 fps). The uniaxial pulling is continued until the samples have fully broken into two parts.

Tunable Failure

Material failure can be tuned by changing material rigidity. To quantify the change from narrow crack to diffuse failure, we measure the dimensionless width of the damage zone, w , defined as the SD of the vertical position of the broken bonds normalized by the lattice spacing. Figs. 1D and 2A and B show w vs. r_i for various sample sizes, illustrating that failure is tunable in all three systems despite the obvious differences in their nature. In all cases, a narrow crack is observed at high rigidity, similar to the failure behavior of a typical brittle elastic solid. In this regime, bonds break in succession in a nearly straight line perpendicular to the direction of applied tension. The small degree to which these thin cracks meander is governed by the disorder in the material (3). However, as the rigidity $r_i \rightarrow 0$, the crack width increases. When $r_i \ll 1$, this width spans the entire system, creating a broad and diffuse failure zone. In this state, bonds break in a nearly uncorrelated fashion until isolated damage zones eventually coalesce to produce a percolating cluster of broken bonds across the sample.

Even though there are large differences in the three systems (static vs. dynamic, central vs. bond-bending forces, nearly ordered vs. highly disordered), in all cases, the failure behavior can be tuned continuously by varying the parameter r_i . This fact remains true even though r_i is controlled in very different ways in the experiments and simulations (changing strut aspect ratio vs. adding additional cross braces as defects or changing the connectivity of a highly disordered system). Reducing r_i marks the approach to an underconstrained mechanical state with vanishing elastic moduli. This state is accompanied by an increasing crack width.

In the case of the experimental system, as a check on the importance of the rigidity transition, we also used a triangular lattice (which remains rigid as $x/a \rightarrow 0$). In this system, w remains constant as $x/a \rightarrow 0$, as shown in Fig. 2B, *Inset*. This finding is in accord with what we would expect if it is the rigidity that controls the failure zone width. Because the triangular lattice remains

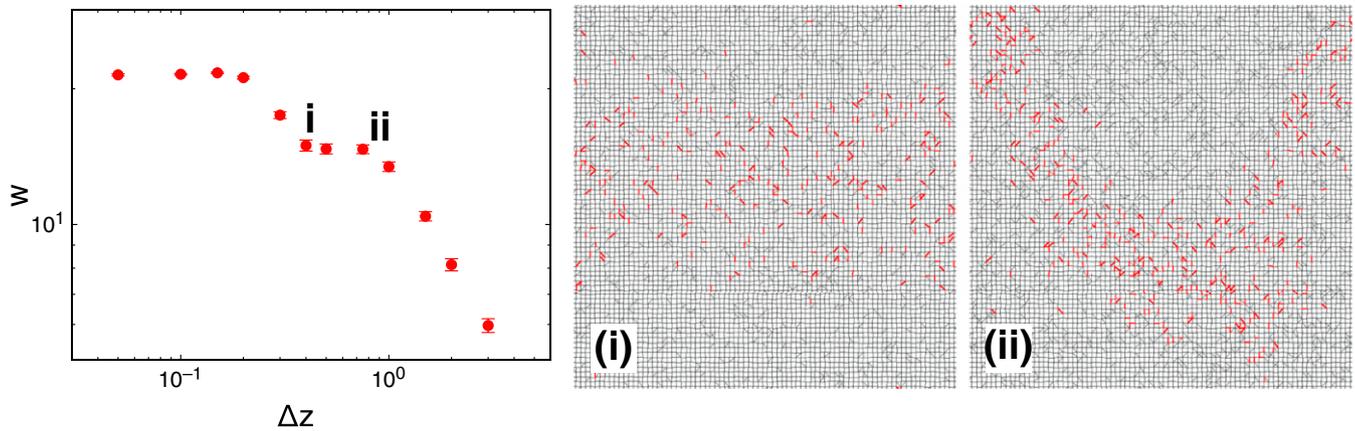


Fig. 3. Crack width vs. Δz in random-network simulations with a square geometry. The images are snapshots at the end of the breaking process for two values of Δz , labeled i and ii on the plot, illustrating the competition between the intrinsic width and the meandering of a crack. The intrinsic crack width is initially the size of the sample and then decreases with increasing Δz . Image (i) shows when the w has first decreased to a second plateau value. As Δz increases further, the intrinsic width decreases and becomes comparable to the meandering width of the crack. Image (ii), at the other end of the plateau, shows a meandering crack with a smaller intrinsic width. At larger Δz , the entire width of the crack decreases.

is least important and in the high Δz limit, one again finds $w \sim r_1^{-1/2}$ (Fig. 2A).

This crossover from intrinsic-dominated to meandering-dominated width is most clearly seen in our largest lateral systems, as illustrated in Fig. 3. [In Fig. 1D, the transverse (horizontal) size was fixed so that meandering did not play an increased role as system size was varied.] As described above, our second simulation system (from which the data in Fig. 3 is obtained) is based on adding cross-braces to a square lattice. Thus, varying Δz not only controls the intrinsic width of a crack by modifying its rigidity but also changes the amount of disorder. Upon increasing Δz even more, the cross-braces are more uniformly distributed throughout the material and the disorder again decreases. Thus, meandering becomes less important at asymptotically high Δz .

We have found that similar diffuse failure at low rigidity also occurs in simulations performed under shear as well as under tension. Due to the small system sizes available in experiments, we are unable to distinguish between meandering and crack-width broadening during material failure. However, our metric for w (SD in broken bonds) allows us to compare simulations and experiment and show the similar behavior in all of the systems we have studied. Sufficiently close to the rigidity transition, failure naturally occurs in a diffuse manner and will encompass the entire system.

A Failure Phase Diagram

Shekhawat et al. (7) have previously considered the transition from crack nucleation to damage percolation in a random fuse network with a distribution of burning thresholds x extracted from a probability distribution $F(x) = x^\beta$ with $\beta > 0$. In the strong disorder limit, $\beta \rightarrow 0$, damage percolation (e.g., diffusive failure) takes place, whereas in the weak disorder limit, $\beta \rightarrow \infty$, crack formation occurs.

In the phase diagram of Fig. 4, we extend that work to include the effects of material rigidity. In addition to β (inversely proportional to disorder) and L (the system size), we include an axis, r , to represent the material rigidity. As a system becomes less and less rigid, the manner in which it fails changes smoothly from a narrow straight crack to broad and diffuse failure. The smooth crossover between regimes is represented schematically where the vertical axis of rigidity is parameterized by r and the horizontal axis of sample length by L . In the limit $L \rightarrow \infty$, cracking always wins over diffuse failure except right at the point where rigidity vanishes.

Unlike our models, the random fuse network is agnostic about the rigidity of the underlying lattice, but the network does mimic the amount of disorder in the breaking thresholds that we have ignored. This finite-size crossover (indicated by a dashed gray line in the horizontal plane of Fig. 4) takes place when $L^{1/\nu_f} \beta$ attains a critical value, with $\nu_f \approx 1.5$ (7). Fig. 4 suggests that the effects of rigidity and disorder can be combined so that different materials can be classified according to their location in a 3D failure “phase diagram.”

The key point is that the divergence of the process zone we observe at the threshold of vanishing rigidity $r = 0$ mirrors what happens in the infinite disorder limit $\beta = 0$. Approaching $r = 0$ acts as a magnifying glass for the effect of disorder. This point is consistent with the suggestion that the jamming transition is “the epitome of disorder,” where there is no length scale on which the system can be averaged to regain an elastic description of the solid (11). Intuitively, the length scale associated with the process zone is a probe of the divergent length scales associated with rigidity loss; failure is the dynamical process that drives the system toward the rigidity transition. Our bond-breaking processes unfold along trajectories of decreasing r in this failure phase

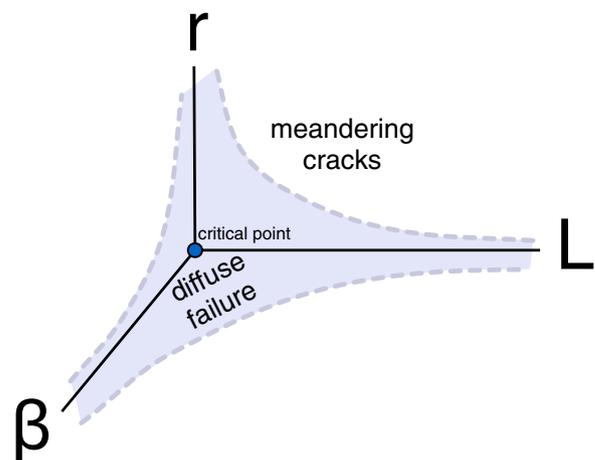


Fig. 4. Schematic fracture phase diagram with three axes: rigidity, r ; system size, L ; and inverse disorder, β . In addition to L and β , rigidity controls the transition between diffusive failure and fracture via narrow meandering cracks.

